

Ultra-high molecular weight polyethylene synthesis using externally modified Si-Mg-Ti Based Z-N catalyst system

Hiren Bhajiwala and Virendrakumar Gupta*

Reliance Research Development Group, Reliance Industries Ltd., Reliance Corporate Park, Ghansoli, Navi Mumbai, Maharashtra – 400701, India

Received: 26 August 2023, Accepted: 1 December 2023

ABSTRACT

Ultra-high molecular weight polyethylene (UHMWPE) was synthesized using Bi-supported $\text{SiO}_2/\text{MgCl}_2/\text{TiCl}_4$ (Si-Mg-Ti) Ziegler-Natta catalyst in conjugation with triethyl aluminum (TEA). The impact of temperature and the presence of a chain-terminating agent were examined in the context of ethylene polymerization. The findings showed that as temperature decreases, the activity of the polymerization decreases, and the molecular weight of the polymer increases. Conversely, in the presence of a chain-terminating agent, the molecular weight of the polymer decreases. The introduction of triethyl borate (TEB) and tetraethoxy silane (TEOS) as an external donor has a pronounced effect on the catalyst activity, causing a significant decrease, while simultaneously leading to a substantial increase in the viscosity average molecular weight (M_v). Additionally, when a chain-terminating agent is added along with triethyl borate (TEB) in the system, it results in a significant decrease in molecular weight, albeit with a slight increase in activity compared to a system without a donor. The crystallinity, particle size and bulk density of the polymer synthesized with and without external donor have been also investigated. **Polyolefins J (2024) 11: 61-70**

Keywords: Si-Mg-Ti Ziegler-Natta catalyst; UHMWPE; ethylene polymerization; external donor.

INTRODUCTION

Ziegler-Natta (Z-N) catalysts have had a significant impact on various aspects of human life over the past few decades, mainly due to their role in the production of high-strength, low-cost, and lightweight polyolefin materials. These materials have contributed to advancements in technology, sustainability, and everyday convenience [1,2]. Polyethylene (PE) and polypropylene (PP) are most common and widely used polyolefin commodity plastics. The combination of their affordability, versatility, and outstanding physical

properties has rendered them indispensable across various industries. Moreover, the continuous increasing demand for polymers in specialty applications has driven scientists and researchers to pursue advanced developments in polymer science and technology [3-5]. In general, advanced Z-N catalyst consists of magnesium dichloride (MgCl_2) support, titanium tetrachloride (TiCl_4) active catalyst, Lewis's base mainly internal donors and external donors and alkyl aluminum activator [6]. Currently, several grades of PP

*Corresponding Author - E-mail: Virendrakumar.Gupta@ril.com

(homo, random, and impact co-polymer-ICP) and PE (high-density polyethylene-HDPE, liner low-density polyethylene-LLDPE, and ultra-high molecular weight polyethylene (UHMWPE)) are commercially producing, by selecting the appropriate components of the Z-N catalyst.

UHMWPE is a liner long chain high molecular weight polymer. It is more commonly used in a specialty application due to its excellent mechanical, chemical, and physical properties. The superior properties of UHMWPE make it comparable to engineering plastics [7-14]. UHMWPE is generally synthesized via several catalyst systems Mg-Ti [15-16], Si-Mg-Ti [17], metallocene [18-19], and post-metallocene [20-23]. However, at commercial scale MgCl₂ supported Z-N catalyst is more popular due to better activity and providing superior product properties [24-26]. Despite, many advantages of Mg-Ti catalyst at the commercial scale, major drawbacks are attrition of catalyst during synthesis which, resulted in fines generation in polymerization, and also poor bulk density which, severely affects plant process [27].

These phenomena were reported in many articles by different scientists. Hence, to overcome the said issue, recently silicon dioxide (SiO₂) and MgCl₂ bi-supported Z-N catalysts reported in many articles for polyethylene synthesis. This catalyst is very much suitable for controlling the particle size of polymers [28-32], which improves catalyst activity as well as morphology significantly [33-36]. Generally, proper selection of catalyst and cocatalyst, donors, plant process parameters and reaction conditions are necessary for the production of UHMWPE [37-39]. Nowadays, internal and external donors play important roles in the polymerization of ethylene and propylene as its greatly influence catalyst activity, hydrogen response, tacticity and end-product properties. Mg-Ti and Si-Mg-Ti-based supported catalyst with internal donor have been reported in many articles for HDPE and UHMWPE synthesis [38-40] but the effect of external donor is still less explored for UHMWPE synthesis.

In this study, we employed a Si-Mg-Ti catalyst for the polymerization of ethylene. This process was conducted in the presence of TEOS within TEB as an external donor, at varying concentrations. Subsequently, we analyzed the influence of these varying concentrations on the polymer resin's molecular weight, thermal behavior, and bulk density.

EXPERIMENTAL

Materials

The silica-supported magnesium titanium Bi-supported SiO₂/MgCl₂/TiCl₄ catalyst (Si-Mg-Ti), with Ti of 2.0 wt.%, Mg of 2.2 wt.%, and mean particle size (D_m) of 9.1 μm , was obtained from Grace and employed without modification for the polymerization of ethylene. n-Decane (99.5 wt.%) and n-hexane (99.5 wt.%) utilized in the polymerization process were sourced from Labort Chemicals in Surat, India. All the solvents were used after drying over a molecular sieve. Co-catalyst triethylaluminium (TEA, 99.5 %) was received from Gudbranson, India. The co-catalyst was used after dilution to 10 v/v%. triethyl borate (TEB, 99 wt.%) and tetraethoxy silane (TEOS, 98.5 %) from Labort Chemicals, India, Surat, were used as external donors for ethylene polymerization. External donors were used after drying over a molecular sieve. Ethylene (purity > 99.9%) for polymerization was obtained from RIL, a commercial polypropylene plant. All the polymerization experiments were carried out in a nitrogen atmosphere.

Polymerization

Ethylene polymerization was conducted in a 4 L high-pressure Parr reactor equipped with a magnetic overhead stirrer, pressure regulator, safety valve, and heating and cooling jacket. A 4 L reactor was heated to 120°C under a nitrogen atmosphere for 2 h, the reactor was evacuated and purged with nitrogen several times and then cooled to 30°C. The reactor was filled with 2 L pre-dried n-hexane as reaction media followed by a small amount of 10 diluted TEAL to kill the moisture in the hexane. To saturate the solvent, the reactor was filled with ethylene for 10 minutes and then discharged. After reducing the pressure of ethylene gas from the reactor, the calculated amount of catalyst, TEAL and charged external donor were injected into the reactor. The polymerization was carried out for 1h with monoester and 2h with a diester catalyst system under 400 rpm stirring and a constant feed of ethylene. The polymer was filtered out and dried at room temperature after the completed reaction.

Characterizations

Molecular weight and viscosity average molecular weight
The polymer's viscosity-average molecular weight (M_v) was determined in decalin at 135°C, following the methodology outlined in the literature [41]. The calculation of M_v was based on the intrinsic viscosity,

employing the Mark-Howink formula mentioned as Equation 1:

$$M_v = 5.34 \times 10^4 [\eta]^{1.49} \quad (1)$$

Thermal analysis

The thermal analysis of the variously synthesized polyethylene samples, employing different catalysts and donors, was carried out using a Differential Scanning Calorimetry (DSC) instrument in a nitrogen atmosphere. Samples weighing between 5 and 8 mg were carefully placed in alumina pans. The temperature was then increased from 30°C to 200°C at a heating rate of 10°C/min, utilizing the Perkin-Elmer model, USA. Additionally, during the cooling phase, the crystallization temperature was recorded, and the cooling rate was maintained at 10°C/min. The crystallinity of polymers was calculated by the following equation [38]:


$$X_c = \Delta H / \Delta H^\circ \times 100 \quad (2)$$

In this context, ΔH signifies the fusion heat for the polyethylene specimen, whereas ΔH° stands for the fusion heat of linear polyethylene, with a value of 290 J/g.

RESULTS AND DISCUSSION

A silica-supported magnesium Ti (Si-Mg-Ti)-based catalyst has been investigated for ethylene polymerization at different temperatures with and without external donors. TEOS and TEB were used as an external donor as shown in Scheme 1. The study included the use of a silica-supported magnesium titanium (Si-Mg-Ti) catalyst for the polymerization of ethylene at varying temperatures, both with and without the inclusion of external donors. Two specific external donors, namely TEOS and TEB are depicted in Scheme 1.

The results of ethylene polymerization using Si-

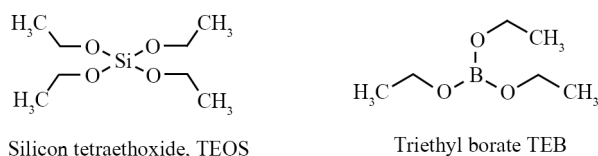

Scheme 1. External donor used with Si-Mg-Ti catalyst for UHMWPE synthesis.

Mg-Ti catalyst in Al/Ti-100 with keeping different temperatures in n-hexane solvent indicate that with increasing temperature, the activity of the catalyst increases significantly. The catalyst activity at 80, 75, 70, 60, and 50°C temperatures was found 10.4, 10.1, 9.7, 4.4, and 2.5 kg_{PE}/g_{cat}, respectively, as shown in Table 1. The observed increase in catalyst activity at higher temperatures can be attributed to the more availability of active centers for polymer growth. This is a common phenomenon in catalysis, where elevated temperatures can enhance the rate of reactions by providing more energy for reactants to interact. However, interesting observation was that at temperatures of 70°C to 80°C, the catalyst activity remains relatively stable, while at temperatures below 70°C, it decreases drastically. This indicates that there might be a temperature threshold or an optimal temperature range at which the catalyst exhibits its highest activity, and beyond which further increases in temperature do not yield significant improvements in activity. This trend revealed that optimal temperature is required to activate the catalyst by alkyl aluminum cocatalyst. The high activity of the catalyst was found for ethylene polymerization due to enough stabilization of Ti⁺³ from Ti⁺⁴ at temperatures between 70 to 80°C.

The molecular weight of the polymer synthesized at 80, 75, 70, 60, and 50°C was determined as 2.3, 2.8, 5.4, 6.1, and 8.8 million, g/mol, respectively, which shows that the molecular weight decreases with increasing temperature. Higher temperature is attributed to the strong chain transfer reaction during polymerization [42-44]. The data in Table 1 reveals an interesting trend, at lower temperatures, specifically at 60°C and 50°C, there is a significant increase in molecular weight, reaching 6.1 and 8.8 million g/mol, respectively. This phenomenon can be attributed to the decrease in temperature in the process of ethylene polymerization using Si-Mg-Ti catalyst, and in this regard, it was found that the molecular weight of the resulting polymer increases significantly due to the lower rate of chain termination compared to chain growth. At reduced temperatures, the catalyst's active sites are more stable, and the slower monomer diffusion to and from these sites allows polymer chains to grow longer before termination. Meanwhile, the overall catalyst activity drops because the diminished thermal energy slows down the reaction kinetics, leading to fewer successful collisions between ethylene molecules and active sites, thereby slowing the rate of polymer formation.

Table 1. Ethylene polymerization using Si-Mg-Ti catalyst at different temperatures in hexane medium^(a).

Run No.	Temp. (°C)	Activity (kg _{PE} /g _{cat})	$M_v^{(b)}$ (million g/mol) ^(b)	BD (T) (g/cm ³)	APS (μm)	Mp (°C)	$X_c^{(c)}$ (%)
1	50	2.5	8.8	0.40	210	135.5	51
2	60	4.4	6.1	0.40	229	134.6	56
3	70	9.7	5.4	0.44	191	134.2	52
4	75	10.1	2.8	0.44	200	133.9	54
5	80	10.4	2.3	0.46	209	133.4	51

^(a) Polymerization conditions: polymerization, time = 2 h, C₂ Pressure = 6 kg/cm², [Al]/[Ti] = 100, Catalyst amount = 70mg, Hydrogen = 0 kg/cm²

^(b) Solution viscosity method using Ubbelohde viscometer

^(c) Crystallinity percent from DSC

Polyethylene produced with the Si-Mg-Ti catalyst exhibits a trend in which the melting point decreases with an increase in the polymerization temperature. Specifically, when polymerization occurred at the low temperature of 50°C, the melting point was observed to be 135.5°C. In contrast, at a higher polymerization temperature of 80°C, the melting point dropped to 133.4°C. The decrease in melting temperature as the polymerization temperature increases is primarily due to the production of polymer chains with lower molecular weights and less regularity in their structure at higher temperatures. Elevated polymerization temperatures can accelerate the reaction kinetics, leading to a higher frequency of chain termination events. This results in shorter polymer chains that are less tightly packed and exhibit a reduced degree of crystallinity and resulted as lower melting temperature. The polymer synthesized using Si-Mg-Ti at different temperatures showed a crystallinity percent between 51 to 56. However, interesting observation was at lowest crystallinity observed at both the highest and lowest polymerization temperatures may be a consequence of different mechanisms. At high temperatures, fast polymerization kinetics prevents the formation of a highly ordered crystalline structure. At low temperatures, the slow polymerization process allows for longer, entangled chains but limits the formation of crystalline regions due to the lack of energy for chain alignment. Lower temperatures typically lead to slower polymerization rates, allowing

more time for the polymer chains to grow longer and become entangled with one another. At higher temperatures, polymerization occurs more rapidly, leading to better-organized structures and higher crystallinity. The tapped bulk density of the polymer slightly decreases as molecular weight increases, which is also a reflection of more entanglement in the polymer. At higher temperatures, crystal alignment in the polymer is more regular compared to entangled higher molecular weight polymer at all temperatures of polymer resin synthesized by modified catalyst system. The average particle size of the polymer resin was found between 190-230 μm (Table 1).

As previously established, hydrogen serves as a widely recognized and effective chain transfer agent for reducing the molecular weight of polymers in olefin polymerization [45-46]. In the catalytic process of ethylene polymerization using Si-Mg-Ti catalysts at an Al/Ti ratio of 100 and 70°C, the incorporation of hydrogen has a marked impact on both the catalyst activity and the molecular weight of the polyethylene produced. The catalytic activity demonstrated a downward trend from 9.7 kg_{PE}/g_{cat} in the absence of hydrogen to 5.0, 5.1, and 0.3 kg_{PE}/g_{cat} as hydrogen concentrations were increased to 240, 320, and 480 ml, respectively (Table 2). The diminishing activity with rising hydrogen levels points to the blocking of active sites by hydrogen, which in turn, limits the availability of ethylene monomers to these sites and promotes the termination reactions [47]. This behaviour is

Table 2. Effect of chain transfer agent in Si-Mg-Ti catalyst for ethylene polymerization at 70°C^(a).

Run No.	Chain transfer agent (Hydrogen, ml)	Activity (kg _{PE} /g _{cat})	$M_v^{(b)}$ (million g/mol) ^(b)	BD (g/cc)	APS (μm)	Mp (°C)	$X_c^{(c)}$ (%)
1	0	9.7	5.4	0.44	191	134.2	52
2	240	5.0	1.8	0.46	175	133.5	48
3	320	5.1	1.4	0.44	235	132.9	50
4	480	0.3	1.1	0.42	75	132.8	52

^(a) Polymerization conditions: polymerization temperature = 80°C, time = 2 h, C₂ Pressure = 6 kg/cm², [Al]/[Ti] = 100, Catalyst amount = 70mg

^(b) Solution viscosity method using Ubbelohde viscometer

^(c) Crystallinity percent from DSC

indicative of the formation of Ti-H bonds, which are characteristically less reactive, and predispose the catalyst to form stabilized Ti-C₂H₅ bonds [46]. Particularly, the catalytic activity remains relatively constant at hydrogen concentrations of 240 and 320 ml, suggesting a partial site blockage by Ti-H bonds [48-51]. However, as hydrogen increases more the activity suddenly decreases drastically, revealing that, Ti-H bond quantity increases significantly and availability of monomer to active site decreases, which suppresses the reaction resulting in lower activity. Parallel to the effect on catalytic activity, the molecular weight of the polymer shows a direct correlation with hydrogen concentration. Absent hydrogen, the molecular weight stands at 5.4 million g/mol, while the introduction of hydrogen at concentrations of 240, 320 and 480 ml results in a reduction of molecular weight to 1.8, 1.4, and 1.1 million g/mol, respectively (Table 2). This decrease in molecular weight confirms the role of hydrogen as a chain transfer agent. Concurrently, the polymer crystallinity was observed to increase a phenomenon attributable to the blocking of catalyst sites by hydrogen [52-53]. This increase in crystallinity could potentially explain the enhanced bulk density of the polymer resin, which was found to be in the range of 0.40 to 0.46 g/cm³ (Table 2). The simultaneous examination of the effects of hydrogen reveals a complex interplay between its inhibitory action on the catalyst active sites, reducing polymerization activity, and its function as a chain transfer agent, diminishing molecular weight. This balance between site-blocking and chain transfer roles of hydrogen is a critical factor in controlling the polymerization process.

In the advance generation Z-N catalysts, internal and external donors play an important role as they control stereo selectivity, catalyst activity, and final polymer properties, which decide end-use applications

[6,38-40]. The high-performance internal donor-based catalysts have gained extensive use in ethylene polymerization processes nowadays. However, it is important to take note that the use of external donors in the context of ethylene polymerization is an area that has not yet received extensive study and investigation. However, some reports [39,54] mentioned the importance of external donors, which influence the molecular weight of the resultant polyethylene, activity of the catalyst, altered the polymer properties, etc. The key working mechanism of external donors is as it alters the electronic and steric environment of the active sites. This modification can lead to a change in the polymer chain growth rate, resulting in longer polymer chains and thus forms higher molecular weights of the polymer. On the other hand, if the external donor suppresses chain transfer reactions, the polymer chain continues to grow longer, leading to increased molecular weight. Additionally, sometimes external donors can reduce the number of active sites available for polymerization by blocking or deactivating them. This leads to decreased catalyst activity since fewer sites are available for ethylene coordination and insertion. The effectiveness of ethylene polymerization employing the Si-Mg-Ti catalyst, in combination with TEOS and TEB external donors, was studied across various donor concentrations. In the absence of an external donor, the catalyst demonstrated an activity of 9.7 kg_{PE}/g_{cat} and a viscosity average molecular weight of 5.4 million g/mol. However, when TEOS external donor was introduced at Al/D ratios of 30, 10 and 2, the activity notably declined to 2.6, 1.0 and 0.5 kg_{PE}/g_{cat}, respectively. A similar observation was found with TEB external donor at Al/D 40, 30 and 10 activities, showing 4.2, 3.0, and 0.2 kg_{PE}/g_{cat}, respectively (Table 3, Figure 1). The decrease in activity indicated that the

Table 3. Effect of external donor on ethylene polymerization using Si-Mg-Ti catalyst at 70°C^(a).

Run No	ED	H ₂ (ml)	Al/D Molar ratio	Activity (kg _{PE} /g _{cat})	M _v ^b (million, g/mol) ^(b)	BD (T) (g/cm ³)	APS (μm)	Mp (°C)	X _c ^(c) (%)
1	-	0	0	9.7	5.4	0.44	191	134.2	52
2	TEOS	0	30	2.6	6.0	0.45	185	134.3	51
3	TEOS	0	10	1.0	8.1	0.37	216	135.1	48
4	TEOS	0	2	0.5	11.0	0.29	240	135.7	47
7	TEB	0	40	4.2	6.6	0.45	190	134.3	50
6	TEB	0	30	3.0	8.4	0.36	183	135.2	50
5	TEB	0	10	0.2	11.7	0.30	222	135.7	47
8	TEB	240	10	1.1	1.9	0.40	160	133.4	50
9	TEB	480	10	0.4	1.7	0.41	166	133.2	48

^(a) Polymerization conditions: polymerization temperature = 70°C, time = 2 h, C₂ Pressure = 6 kg/cm², [Al]/[Ti] = 100, Catalyst amount = 70 mg

^(b) Solution viscosity method using Ubbelohde viscometer

^(c) Crystallinity percent from DSC

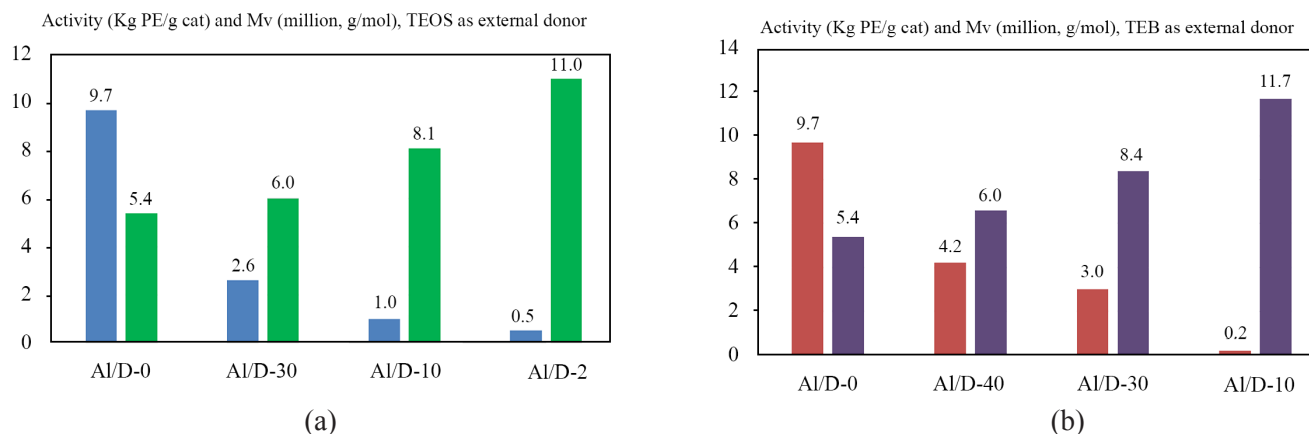


Figure 1. Effect of TOES and TEB external donor on Si-Mg-Ti catalyst activity and molecular weight of UHMWPE.

external donor blocks the active site of the polymer. In addition, due to their bulky group molecular structures, TEOS and TEB introduce steric hindrance a phenomenon where bulky groups within a molecule block the active sites by their sheer size. This hindrance leads to less frequent successful additions of ethylene units, thereby decreasing the catalyst's overall activity in forming polyethylene. Such steric limitations can slow down the rate of polymer formation and alter the polymer's structure and properties. By fine-tuning the concentration of these external donors, the catalytic process can be fine-tuned, and the properties of the polyethylene produced can be customized [55-57]. Moreover, the configuration of the external donor is a crucial factor influencing the activity of the Si-Mg-Ti catalyst. In the case of TEOS, where four ethoxy groups are connected to silicon, it exhibited lower activity in comparison to TEB, which has three alkoxy groups linked to boron (B). This observation suggests that a higher number of alkoxy groups effectively deactivate the active centers of the catalyst [58].

The molecular weight of the polymer synthesized with and without external donor results shown in Table 3 indicate that external donor significantly affects the molecular weight of polyethylene. In ethylene polymerization without a donor, the molecular weight was determined to be 5.4 million g/mol. However, when using TEOS as the external donor at Al/D ratios of 30, 10 and 2, the molecular weight increased to 6.0, 8.1, and 11.1 million g/mol, respectively. Similarly, with TEB as the external donor at Al/D ratios of 40, 30, and 10, the molecular weight was measured at 6.6, 8.4 and 11.7 million g/mol, respectively (Table 3, Figure 1). These results demonstrate the significant influence of external donors on the molecular weight of the synthesized polyethylene. The significant increases

in molecular weight and simultaneously decreases in activity observed in the presence of external donors indicate a reduction in chain termination as the donor concentration increases. An interesting observation showed that with TEOS as the external donor, the molecular weight was extremely high, reaching 11.0 million g/mol with an Al/D ratio of 2. Conversely, when TEB was used as the external donor at an Al/D ratio of 10, the molecular weight reached 11.7 million g/mol. This showcases the remarkable impact of external donors on increases of the molecular weight of the polymer. The higher molecular weight and lower activity with lower donor consumption in the case of TEB compared to TEOS revealed that TEB required less amount of donor to block the active sites on the catalyst after a certain concentration of donor. Also, during the polymerization reaction, external and co-catalyst make complex and bind to the catalyst surface, which reduced the active center on the catalyst surface compared to the 'donor-free' system, which reflected a reduction in catalyst activity [59]. Interestingly, at the same time external donors were not allowed chain termination faster, which resulted in a higher molecular weight polymer generation.

The bulk density results of the polymer synthesized using TEOS and TEB external donor shown in the table indicate that as molecular weight increases, the bulk density decreases significantly compared to donor-free system. The bulk density without donor was found 0.45 g/cm³, whereas, with increased concentration of TEOS, it was observed between 0.45 to 0.29 g/cm³, and in the case of TEB it was between 0.45 to 0.30 g/cm³. The results clearly indicate the relation between molecular weight and bulk density of polymer resin. A decrease in the bulk density of the high molecular weight polymer occurred due to

greater entanglement of the polymer chain compared to chain alignment in the donor-free polymer. The APS of the resin synthesized with TEOS and TEB donor increases with increasing donor concentration and is higher compared to the resin was prepared by the donor-free catalyst system. The crystallinity percent of the polymer decreases as donor concentration increases in both TEOS and TEB external donors. The results shown in Table 3 indicate that there is a relation between crystallinity percent and molecular weight, as molecular weight increases the crystallinity percent decreases. The results exhibited that donor-free catalyst system has a short polymer chain compared to a polymer synthesized using an external donor. The long chain always has more entanglement compared to the short chain polymer, which reflects a lowering of the crystallinity compared to with donor system (Table 3).

The effect of different concentrations of chain-terminating agents during ethylene polymerization was investigated with Si-Mg-Ti catalyst and TEB external donor. The results shown in Table 3 indicate that at 240 ml and 480 ml hydrogen concentration, activity increases slightly 1.1 and 0.4 $\text{kg}_{\text{PE}}/\text{g}_{\text{cat}}$ compared to without hydrogen 0.2 $\text{kg}_{\text{PE}}/\text{g}_{\text{cat}}$. However, molecular weight decreases significantly from 11.7 million g/mol to 1.9 and 1.7 million g/mol, respectively. This is due to the higher hydrogen response of the catalyst, as well as the increased rate of chain termination in the active center, which is reflected in the decrease in the molecular weight of polyethylene. [60]. The crystallinity percent of the polymer was found 50% and 48% which is slightly higher compared to the polymer synthesized without hydrogen. The bulk density of the polymer increases as chain transfer agent concentration increases.

CONCLUSION

In conclusion, the Si-Mg-Ti catalyst for ethylene polymerization at different temperatures provides polyethylene with different scales of higher molecular weight polyethylene. The molecular weight increases with decreases in the polymerization temperature. However, Si-Mg-Ti is highly active for ethylene polymerization between 70 to 80°C, below that activity decreases drastically. The utilization of TEOS and TEB as external donors at different concentrations with Si-Mg-Ti catalyst for ethylene polymerization leads

to decreases activity but at the same time increases viscosity average molecular weight significantly. The catalyst's responsiveness to hydrogen is marked, evidenced by a considerable reduction in molecular weight when a chain-terminating agent is present, as opposed to molecular weight without chain terminating agent. The bulk density of polyethylene is higher in cases without a donor, and it decreases with increases in the molecular weight of polymer. The modification of the catalyst with external donors for ethylene polymerization provides a straightforward and cost-effective method for producing very high molecular weight polyethylene. This advancement opens opportunities for niche applications.

ACKNOWLEDGEMENTS

We would like to express our sincere gratitude to Reliance Industries Limited for their invaluable support and for providing the opportunity to undertake this research. We are also grateful for the contribution of an analytical team to support for analysis.

CONFLICTS OF INTEREST

The authors declare that they have no conflicts of interest.

REFERENCES

- 1 Sauter DW, Popoff N, Bashir MA, Szeto KC, Gauvin RM, Delevoye L, Taoufik M, Boisson C (2016) The design of a bipodal bis(pentafluorophenoxy)aluminate supported on silica as an activator for ethylene polymerization using surface organometallic chemistry. *Chem Comm* 52: 4776-4779
- 2 Wang X, Han X, Ren F, Xu R, Bai Y (2018) Porous organic polymers-supported metallocene catalysts for ethylene/1-hexene copolymerization. *Catalysts* 8: 146
- 3 Sauter DW, Taoufik M, Boisson C (2017) Polyolefins, a success story. *Polymers* 9: 185
- 4 Salamone JC, (1996) *Polymeric materials encyclopedia*, vol.6, CRC, Boca Raton (FL)
- 5 Zhu L, He X, Cheng R, Liu Z, Zhao N, Liu B (2018) Effects of Ti/Mg molar ratio on bi-

- supported $\text{SiO}_2/\text{MgCl}_2$ (ethoxide type)/ TiCl_4 catalysts in ethylene homo polymerization and ethylene/1-hexene copolymerization. *Polyolefins J* 5: 1-13
- 6 Kumawat J, Gupta VK (2020) Fundamental aspects of heterogeneous Ziegler–Natta olefin polymerization catalysis: an experimental and computational overview. *Polym Chem* 11: 6107-6128
- 7 Peacock AJ (2000) *Handbook of polyethylene*, Marcel & Dekker, New York
- 8 Abdul Samad M (2021) Recent advances in UHMWPE/UHMWPE nanocomposite/UHMWPE hybrid nanocomposite polymer coatings for tribological applications: A comprehensive review. *Polymers* 13: 608
- 9 Xiao CF, Zhang YF, An SL, Jia GX (2000) Structural changes of gel drawn, ultra-high molecular weight polyethylene fibers with kerosene as a solvent. *Polym Eng Sci* 40: 238-246
- 10 Smith P, Lemstra PJ, Booi HC (1981) Ultra drawing of high-molecular-weight polyethylene cast from solution. II. Influence of initial polymer concentration. *J Polym Sci Pol Phys Ed* 19: 877-888
- 11 Xiao CF, Zhang YF, An SL, Jia G (1996) Investigation on the thermal behaviors and mechanical properties of ultrahigh molecular weight polyethylene (UHMW-PE) fibers. *J Appl Polym Sci* 59: 931-935
- 12 Jamjah R, Zohuri GH, Javaheri M, Nekoomanesh M, Ahmadjo S, Farhadi A (2008) Synthesizing UHMWPE Using Ziegler-Natta Catalyst System of MgCl_2 (ethoxide type)/ TiCl_4 /triisobutylaluminum. *Macromol Symp* 274: 148-153
- 13 Zohuri GH, Damavandi S, Ahmadjo S, Sandaroos R, Shamekhi MA (2014) Synthesis of high molecular weight polyethylene using FI catalyst. *Polyolefins J* 1: 25-32
- 14 Damavandi S, Samadieh N, Ahmadjo S, Etemadinia Z, Zohuri GH (2015) Novel Ni-based FI catalyst for ethylene polymerization. *Eur Polym J* 64: 118-125
- 15 Jones RL, Armoush M (2009) Catalysts for UHMWPE. *Macromol Symp* 283-284: 88-95
- 16 Padmanabhan S, Sarma K R, Rupak K, Sharma S (2010) Synthesis of ultra-high molecular weight polyethylene: A differentiate material for specialty applications. *Mater Sci Eng B* 168: 132-135
- 17 Zohuri G, Bonakdar MA, Damavandi S, Eftekhari M, Askari M, Ahmadjo S (2009) Preparation of ultra high molecular weight polyethylene using bi-supported $\text{SiO}_2/\text{MgCl}_2$ (spherical)/ TiCl_4 Catalyst: A morphological study. *Iran Polym J* 18: 593-600
- 18 Kaminsky W, Engehausen R, Zoumis K, Spaleck W, Rohrmann J (1992) Standardized polymerizations of ethylene and propene with bridged and unbridged metallocene derivatives: A comparison. *Makromol Chem* 193: 1643-1651
- 19 Reddy SS, Sivaram S (1995) Homogeneous metallocene-methylaluminoxane catalyst systems for ethylene polymerization. *Prog Polym Sci* 20: 309-367
- 20 Makio H, Terao H, Iwashita A, Fujita T (2011) FI catalysts for olefin polymerization: A comprehensive treatment. *Chem Rev* 111: 2363-2449
- 21 Matsugi T, Fujita T (2008) High-performance olefin polymerization catalysts discovered on the basis of a new catalyst design concept. *Chem Soc Rev* 37: 1264-1277
- 22 Chikkali SH, Patel K, Netalkar S, (2017) Insertion or Ziegler–Natta polymerization of olefins. In: *Metal-catalyzed polymerization*, CRC press, Boca Rotan, 31-115
- 23 Wang Y, Fan H, Jie S, Li BG (2014) Synthesis and characterization of titanium (IV) complexes bearing end functionalized biphenyl: Efficient catalysts for synthesizing high molecular weight polyethylene. *Inorg Chem Commun* 41: 68-71
- 24 Soga K, Shiono T (1997) Ziegler-Natta catalysts for olefin polymerizations. *Prog Polym Sci* 22: 1503-1546
- 25 Liu Z, Zhang H (2022) Ultra-high molecular weight polyethylene: Preparation and applications. *J Phys Conf Series* 2229: 012006
- 26 Galli P, Vecellio G (2001) Technology: Driving force behind innovation and growth of polyolefins. *Prog Polym Sci* 26: 1287-1336
- 27 Abboud M, Denifl P, Reichert KH (2005) Fragmentation of Ziegler-Natta catalyst particles during propylene polymerization. *Macromol Mater Eng* 290: 558-564
- 28 Jamjah R, Zohuri GH, Vaezi J, Ahmadjo S, Nekoomanesh M, Pouryari M (2006) Morphological study of spherical $\text{MgCl}_2 \cdot n\text{EtOH}$

- supported TiCl_4 Ziegler-Natta catalyst for polymerization of ethylene. *J Appl Polym Sci* 101: 3829-3834
- 29 Zohuri GH, Jamjah R, Ahmadjo S (2006) Comparative study of propylene polymerization using monosupported and bisupported titanium-based Ziegler-Natta catalysts. *J Appl Polym Sci*, 100: 2220-2226
- 30 Barbe PC, Cecchin G, Noristi L (1986) The catalytic system Ti-complex/ MgCl_2 . *Adv Polym Sci* 81: 1-81
- 31 Silva FM, Broyer JP, Novat C, Lima EL, Pints JC, Mckenna TF, (2005) Investigation of catalyst fragmentation in gas-phase olefin polymerization: A novel short stop reactor. *Macromol Rapid Commun* 20: 1846-1853
- 32 Shaotian W, Liu JC, Make MP, Lee CC (2001) Ethylene polymerization process, US Patent 625,541,5
- 33 Galli P, Vecellio G (2004) Polyolefins: The most promising large-volume materials for the 21st century. *J Polym Sci Pol Chem* 42: 396-415
- 34 Fukuda K, Liu B, Nakatani H, Nishiyama I, Yamahiro M, Terano M (2003) Significant variation of molecular weight distribution (MWD) of polyethylene induced by different alkyl-Al co-catalysts using a novel surface functionalized SiO_2 -supported Ziegler-Natta catalyst. *Catal Commun* 4: 657-662
- 35 Zohuri GH, Azimfar F, Jamjah R, Ahmadjo S (2003) Polymerization of propylene using the high-activity Ziegler-Natta catalyst system $\text{SiO}_2/\text{MgCl}_2$ (ethoxide type)/ TiCl_4 /Di-n-butyl phthalate/triethylaluminum/dimethoxy methyl cyclohexyl silane. *J Appl Polym Sci* 89: 1177-1181
- 36 Zohuri GH, Ahmadjo S, Jamjah R, Nekoomanesh M (2001) Structural study of mono and bi-supported Ziegler-Natta catalysts of $\text{MgCl}_2/\text{SiO}_2/\text{TiCl}_4$ /donor systems. *Iran Polym J* 10: 149-155
- 37 Jones RL, Armoush MZ, Harjati T, Elder M, Hummel AA, Sullivan J (2010). Catalysts for UHMWPE and UHMWPE-copolymers. *Inorg Chim Acta* 364: 275-281
- 38 Shin YJ, Zhang HX, Yoon KB, Lee DH (2010) Preparation of ultra-high molecular weight polyethylene with $\text{MgCl}_2/\text{TiCl}_4$ catalysts: Effect of temperature and pressure. *Macromol Res* 18: 951-955
- 39 Zhang HX, Shin YJ, Lee DH, Yoon KB (2011) Preparation of ultra-high molecular weight polyethylene with $\text{MgCl}_2/\text{TiCl}_4$ catalyst: effect of internal and external donor on molecular weight and molecular weight distribution. *Polym Bull* 66: 627-635
- 40 Zhang HX, Shin YJ, Lee DH, Yoon KB (2012) Preparation of ultra-high molecular weight polyethylene with $\text{MgCl}_2/\text{TiCl}_4$ catalyst: Effect of hydrogen and cocatalyst on molecular weight and molecular weight distribution. *Macromol Res* 20: 112-115
- 41 Hasebe K, Fujiwara A, Nozaki T, Miyamoto K (2007) Ultrahigh molecular weight ethene copolymers from metallocene and Ziegler catalysts. *Macromol Symp* 260: 161-164
- 42 Kojoh SI, Kioka M, Kashiwa N, Itoh M, Mizuno A (1995) A study of chain-end structures of polypropylene prepared with MgCl_2 -supported titanium catalyst. *Polymer* 36: 5015-5018
- 43 Kojoh SI, Kioka M, Kashiwa N (1999) The influences of cocatalyst on propylene polymerization at high temperature with a MgCl_2 -supported TiCl_4 catalyst system. *Eur Polym J* 35: 751-755
- 44 Zohuri G, Jamjah R, Mehtarani R, Nekoomanesh Haghighi M, Ahmadjo S (2003) Slurry polymerization of ethylene using bi-supported Ziegler-Natta catalyst of $\text{SiO}_2/\text{MgCl}_2$ (ethoxide type) TiCl_4 /TEA system. *Iran Polym J* 12: 31-36
- 45 Zhang B, Fu Z, Fan Z, Phiriyawirut P, Charoenchaidet S (2016) Preparation and characterization of high MFR polypropylene and polypropylene/poly (ethylene-co-propylene) in-reactor alloys. *J Polym Sci* 133: 42984
- 46 Kissin YV (2001) Main kinetic features of ethylene polymerization reactions with heterogeneous Ziegler-Natta catalysts in the light of a multicenter reaction mechanism. *J Polym Sci Pol Chem* 39: 1681-1695
- 47 Parvez MA, Rahaman M, Suleiman M, Soares JB, Hussein IA (2014) Correlation of polymerization conditions with thermal and mechanical properties of polyethylenes made with Ziegler-Natta catalysts. *Int J Polym Sci*: 549031
- 48 Garoff T, Johansson S, Pesonen K, Waldvogel P, Lindgren D (2002) Decrease in activity caused by hydrogen in Ziegler-Natta ethene polymerization. *Eur Polym J* 38: 121-132
- 49 Kissin YV, Mink RI, Nowlin TE (1999) Ethylene polymerization reactions with Ziegler-Natta

- catalysts. I. Ethylene polymerization kinetics and kinetic mechanism. *J Polym Sci Pol Chem* 37: 4255-4272
- 50 Chu KJ, Soares JB, Penlidis A (2000) Effect of hydrogen on ethylene polymerization using in-situ supported metallocene catalysts. *Macromol Chem Phys* 201: 552-557
- 51 Niyomthai T, Ratchadaphet A, Jongsomjit B, Praserttham P (2018) Influence of hydrogen on catalytic properties of Ziegler-Natta catalysts prepared by different methods in ethylene polymerization. *Adv Polym Tech* 37: 1035-1040
- 52 Czaja K, Białek M (2001) Effect of hydrogen on the ethylene polymerization process over Ziegler-Natta catalysts supported on $MgCl_2(THF)_2$. I. Studies of the chain-transfer reaction *J Appl Polym Sci* 79: 356-360
- 53 Munoz-Escalona A, Parada A (1979) Factors affecting the nascent structure and morphology of polyethylene obtained by heterogeneous Ziegler-Natta catalysts: 2. Crystallinity and melting behaviour. *Polymer* 20: 859-866
- 54 Trivedi PM, Gocher CP, Balachandran V, Gupta VK (2023) Insight of polypropylene synthesis with high performance multidentate internal donor catalyst system. *J Appl Polym Sci* 140: e53609
- 55 Sacchi MC, Forlini F, Tritto I, Locatelli P, Morini G, Noristi L, Albizzati E (1996) Polymerization stereochemistry with Ziegler-Natta catalysts containing dialkylpropane diethers: A tool for understanding internal/external donor relationships. *Macromolecules* 29: 3341-3345
- 56 Li P, Tu S, Xu T, Fu Z, Fan Z (2015) The influence of combined external donor and combined cocatalyst on propylene polymerization with a $MgCl_2$ -supported Ziegler-Natta catalyst in the presence of hydrogen. *J Appl Polym Sci* 132: 41689
- 57 Song BG, Ihm SK (2014) The role of two different internal donors (phthalate and 1,3-diether) on the formation of surface structure in $MgCl_2$ -supported Ziegler-Natta catalysts and their catalytic performance of propylene polymerization. *J Appl Polym Sci* 31: 40536
- 58 Zhang H-X, Lee Y-J, Park J-R, Lee D-H, Yoon K-B, (2011) Control of molecular weight distribution for polypropylene obtained by commercial Ziegler-Natta catalyst: Effect of electron donor. *Macromol Res* 19: 622-628
- 59 Niyomthai T, Jongsomjit B, Praserttham P (2017) Investigation of Alkoxysilanes in the Presence of Hydrogen with Ziegler-Natta Catalysts in Ethylene Polymerization. *Eng J* 21: 171-180
- 60 Thongdonjui A, Trakarnpruk W, Strauss RH (2009) Effect of Electron Donor on PE Polymerization. *J Met Mater Miner* 19: 17-23